

Spin-parity dependent tunneling of magnetization in single-molecule magnets

W. Wernsdorfer¹, S. Bhaduri², C. Boskovic², G. Christou², D.N. Hendrickson³

¹*Lab. L. Néel, associé à l'UJF, CNRS, BP 166, 38042 Grenoble Cedex 9, France*

²*Dept. of Chemistry and Molecular Structure Center,
Indiana Uni., Bloomington, 47405-4001, IN, USA*

³*Dept. of Chemistry and Biochemistry, Uni. of California at San Diego, La Jolla, 92037, CA, USA*

(Dated: February 1, 2008)

Single-molecule magnets facilitate the study of quantum tunneling of magnetization at the mesoscopic level. The spin-parity effect is among the fundamental predictions that have yet to be clearly observed. It is predicted that quantum tunneling is suppressed at zero transverse field if the total spin of the magnetic system is half-integer (Kramers degeneracy) but is allowed in integer spin systems. The Landau-Zener method is used to measure the tunnel splitting as a function of transverse field. Spin-parity dependent tunneling is established by comparing the transverse field dependence of the tunnel splitting of integer and half-integer spin systems.

PACS numbers: PACS numbers: 75.45.+j, 75.60.Ej

Single-molecule magnets (SMM) are considered the best systems for studying quantum tunneling of magnetization at the mesoscopic level. The first molecule shown to be a SMM was Mn_{12} acetate [1]. It exhibits slow magnetization relaxation of its $S = 10$ ground state which is split by axial zero-field splitting. It was the first system to show thermally assisted tunneling of magnetization [2, 3, 4]. Fe_8 and Mn_4 SMMs were the first to exhibit ground state tunneling [5, 6]. Tunneling was also found in other SMMs (see, for instance, [7, 8, 9]). A detailed study of the influence of environmental degrees of freedom on the tunnel process has been started on Fe_8 and Mn_{12} acetate (concerning phonons [10, 11], nuclear spins and dipolar couplings [12, 13, 14]) which were motivated by theories [15, 16, 17]. The spin-parity effect is among the fundamental predictions which have yet to be established at the mesoscopic level. It is predicted that quantum tunneling is suppressed at zero applied field if the total spin of the magnetic system is half-integer but is allowed in integer spin systems. Van Hemmen and Sütö [18] were the first to suggest the absence of tunneling as a consequence of Kramers degeneracy [35]. It was then shown that tunneling can even be absent without Kramers degeneracy [19, 20, 21]. In this case, quantum phase interference can lead to destructive interference and thus suppress tunneling [21]. This effect was recently seen in Fe_8 and Mn_{12} SMMs [22, 23].

There are several reasons why the first attempts [6, 24] to observe the spin-parity effect were unsuccessful. The main reason reflects the influence of environmental degrees of freedom that can induce or suppress tunneling: Firstly, hyperfine and dipolar couplings can induce tunneling via transverse field components; furthermore, intermolecular superexchange coupling may enhance or suppress tunneling depending on its strength; phonons can induce transitions via excited states; and finally, faster relaxing species can complicate the interpretation [13].

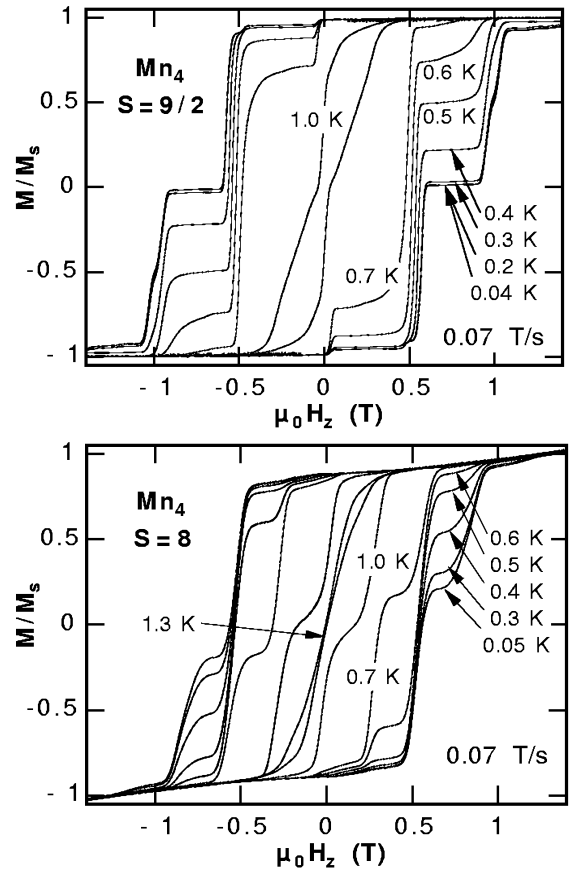


FIG. 1: Hysteresis loops of a single crystal of (a) Mn_4 ($S=9/2$) and (b) Mn_4 ($S=8$) molecular clusters at different temperatures and a constant field sweep rate $dH_z/dt = 0.07$ T/s.

In this letter, we show that these problems can be overcome by studying the tunnel splitting as a function of transverse field. We selected three SMMs which revealed to be sufficiently small to show clearly ground state tunneling.

The first is $[\text{Mn}_4\text{O}_3(\text{OSiMe}_3)(\text{OAc})_3(\text{dbm})_3]$, called Mn_4 -($S = 9/2$), with a half-integer ground state $S = 9/2$. The second is $[\text{Mn}_4(\text{O}_2\text{CMe})_2(\text{Hpdm})_6][\text{ClO}_4]_2$, called Mn_4 -($S = 8$), with an integer ground state $S = 8$. The third is the well known Fe_8 SMM with a $S = 10$ spin ground state [5]. The preparation, X-ray structure, and detailed physical characterization of both Mn_4 molecules have been presented [9, 25]. The complex Mn_4 -($S = 9/2$) crystallizes in a hexagonal space group with a crystallographic C_{3v} symmetry. The complex has a trigonal-pyramidal (highly distorted cubane-like) geometry. This complex is mixed-valent: $\text{Mn}_3^{\text{III}}\text{Mn}^{\text{IV}}$. The C_{3v} axis passes through the Mn^{IV} ion and the triply bridging siloxide group. DC and AC magnetic susceptibility measurements indicate a well isolated $S = 9/2$ ground state [25]. The complex Mn_4 -($S = 8$) crystallizes in a triclinic lattice. The cation lies on an inversion center and consists of a planar Mn_4 rhombus that is also mixed-valent: $\text{Mn}_2^{\text{III}}\text{Mn}_2^{\text{II}}$. DC and AC magnetic susceptibility measurements indicate a $S = 8$ ground state [9].

All measurements were performed using an array of micro-SQUIDS [12]. The high sensitivity of this magnetometer allows us to study single crystals of SMMs of sizes of the order of 10 to 500 μm . The field can be applied in any direction by separately driving three orthogonal coils.

Before presenting our measurements we review briefly the giant spin model which is the simplest model describing the spin system of SMMs. The spin Hamiltonian is

$$H = -DS_z^2 + H_{\text{trans}} + g\mu_B\mu_0\vec{S} \cdot \vec{H} \quad (1)$$

S_x , S_y , and S_z are the three components of the spin operator; D is the anisotropy constant defining an Ising type of anisotropy; H_{trans} , containing S_x or S_y spin operators, gives the transverse anisotropy which is small compared to DS_z^2 in SMMs; and the last term describes the Zeeman energy associated with an applied field $\vec{H}$. This Hamiltonian has an energy level spectrum with $(2S+1)$ values which, to a first approximation, can be labeled by the quantum numbers $m = -S, -(S-1), \dots, S$ taking the z -axis as the quantization axis. The energy spectrum can be obtained by using standard diagonalization techniques. At $\vec{H} = 0$, the levels $m = \pm S$ have the lowest energy. When a field H_z is applied, the levels with $m < 0$ increase in energy, while those with $m > 0$ decrease. Therefore, energy levels of positive and negative quantum numbers cross at certain values of H_z . It turns out that the levels cross at fields given by $\mu_0 H_z \approx nD/g\mu_B$, with $n = 0, 1, 2, 3, \dots$

When the spin Hamiltonian contains transverse terms (H_{trans}), the level crossings can be “avoided level crossings”. The spin S is “in resonance” between two states when the local longitudinal field is close to an avoided level crossing. The energy gap, the so-called “tunnel splitting” Δ , can be tuned by a transverse field (a field

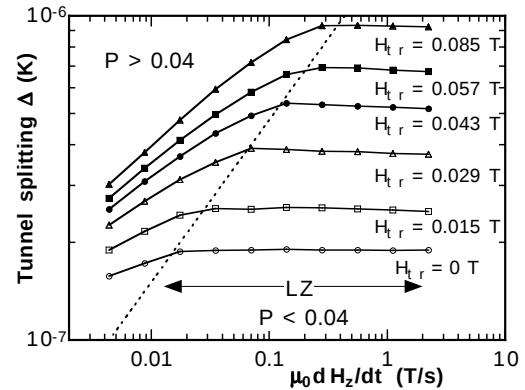


FIG. 2: Field sweeping rate dependence of the tunnel splitting $\Delta_{-9/2,9/2}$ measured by a Landau-Zener method for a Mn_4 -($S=9/2$) samples, at different transverse fields. The Landau-Zener method works in the region of high sweeping rates where $\Delta_{-9/2,9/2}$ is sweeping rate independent.

applied perpendicular to the S_z direction) via the $S_x H_x$ and $S_y H_y$ Zeeman terms.

The effect of these avoided level crossings can be seen in hysteresis loop measurements. Figs. 1a and 1b show typical hysteresis loop measurements for single crystals of Mn_4 -($S = 9/2$) and Mn_4 -($S = 8$) (for Fe_8 data, see [12]). When the applied field is near an avoided level crossing, the magnetization relaxes faster, yielding steps separated by plateaus. As the temperature is lowered, there is a decrease in the transition rate due to reduced thermally assisted tunneling. A similar behavior was observed in Mn_{12} acetate clusters [2, 3, 4]. As seen for Fe_8 hysteresis loops become temperature-independent below 0.4 K indicating ground state tunneling. The field between two resonances allows us to estimate the anisotropy constants D . We obtain 0.68 K and 0.43 K for Mn_4 -($S = 9/2$) and Mn_4 -($S = 8$), respectively.

In order to establish the spin-parity effect, the tunnel splitting was measured as a function of transverse field. The field dependence of the tunnel splitting is expected to be very sensitively dependent on the spin-parity and the parity of the avoided level crossing. This approach is based on the Landau-Zener model that describes the nonadiabatic transition between the two states in a two-level system [26, 27]. The original work by Zener concentrated on the electronic states of a diatomic molecule, while Landau considered two atoms that undergo a scattering process. Their solution of the time-dependent Schrödinger equation of a two-level system can be applied to many physical systems and it has become an important tool for studying tunneling transitions. The Landau-Zener model has also been applied to spin tunneling in nanoparticles and clusters [28, 29, 30, 31, 32].

When sweeping the longitudinal field H_z at a constant rate over an avoided energy level crossing, the tunneling

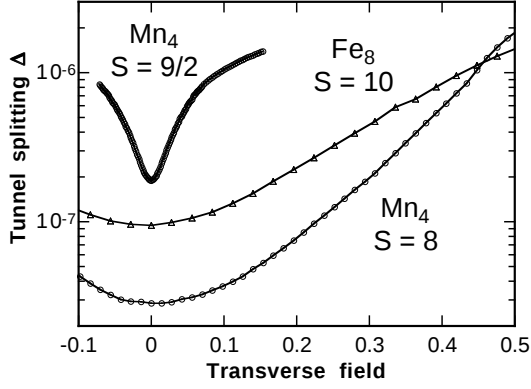


FIG. 3: Tunnel splitting for three SMMs as a function of transverse field. The data for Fe_8 were taken from [22] with the transverse field applied along the medium hard axis.

probability P is given by

$$P_{m,m'} = 1 - \exp \left[-\frac{\pi \Delta_{m,m'}^2}{2\hbar g \mu_B |m - m'| \mu_0 dH_z/dt} \right] \quad (2)$$

Here, m and m' are the quantum numbers of the avoided level crossing, dH_z/dt is the constant field sweep rate, $g \approx 2$, μ_B is the Bohr magneton, and $\hbar$ is Planck's constant.

In order to apply quantitatively the Landau-Zener formula (Eq. 2), we first checked the predicted sweep field dependence of the tunneling rate. The SMM crystal was first placed in a high negative field to saturate the magnetization. Then, the applied field was swept at a constant rate over one of the resonance transitions and the fraction of molecules that reversed their spin was measured. The tunnel splitting Δ was calculated using Eq. 2 and is plotted in Fig. 2 as a function of field sweep rate. The Landau-Zener method is applicable in the region of high sweep rates where $\Delta_{-9/2,9/2}$ is independent of sweep rate. The deviations at lower sweeping rates are mainly due to the *hole-digging mechanism* [12] as observed for Fe_8 SMM [11]. Such behavior has recently been simulated [33] [36].

Fig. 3 presents the measured tunnel splittings obtained by the Landau-Zener method as a function of transverse field. Note that for all three SMMs the tunnel splitting is finite. However, depending on the spin-parity the sensitivity to an applied transverse field is completely different. The tunnel splitting increases gradually for an integer spin, whereas it increases rapidly for a half-integer spin. Note also that Δ is plotted on a logarithmic scale in Fig. 3, and that the tunnel probability should depend on the second power of Δ (Eq. 2). Therefore, our measurements show that the tunneling rate of a half-integer spin is strongly transverse field dependent, unlike the case for

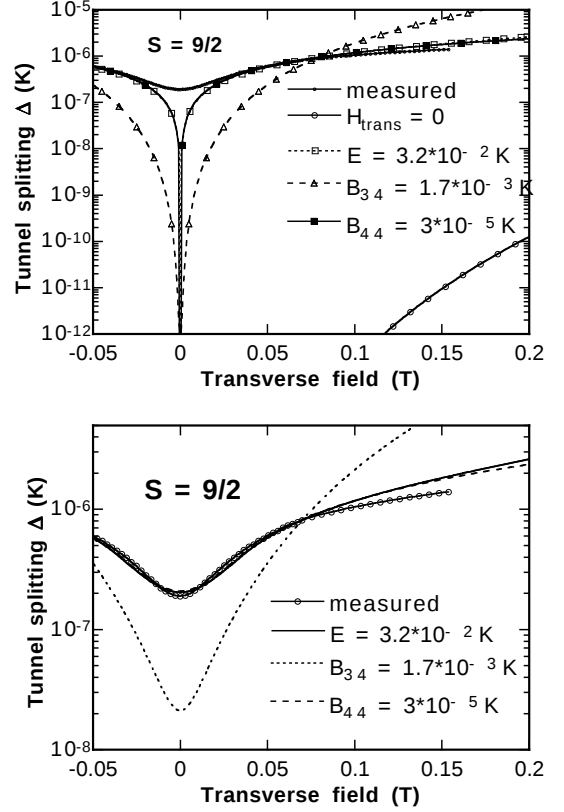


FIG. 4: (a) First attempt to simulated the measured tunnel splittings for Mn_4 ($S = 9/2$). For simplicity, the calculated Δ has been averaged over all possible orientation of the transverse field. (b) Same as in (a) but taking into account a Gaussian distribution of transverse field components with a half-width $\sigma = 0.035$ T.

an integer spin SMM.

Figs. 4a and 4b present the first attempt to simulate the measured tunnel splittings for Mn_4 ($S = 9/2$). Firstly, one should note that there must be transverse terms in the spin Hamiltonian because for $H_{\text{trans}} = 0$, the measured tunnel splitting should be orders of magnitude smaller than observed. Secondly, we tried to simulate the data with a transverse term $(B_{34}/2 * [S_z(S_+^3 + S_-^3) + (S_+^3 + S_-^3)S_z])$ with respect to the C_3 symmetry of the SMM. However, this term also cannot account for the measured tunnel splitting. Finally, we found that either the second order term $(E * (S_+^2 + S_-^2))$ or a fourth order term $(B_{44} * (S_+^4 + S_-^4))$ can equally well describe the measurements [37]. These results suggest that there is a small effect which breaks the C_3 symmetry. This could be a small strain inside the SMM crystal induced by defects. Such defects could result from either a loss of solvent molecules or dislocations [34].

In the ideal case, one would expect $\Delta = 0$ for $\vec{H} = 0$. This is not found in a real SMM because of the influence of environmental degrees of freedom that can induce

tunneling. In our case, mainly hyperfine and dipolar couplings induce tunneling via transverse field components. Fig. 4b presents a simulation of the measured tunnel splitting when taking into account a Gaussian distribution of transverse field components with a width $\sigma = 0.035$ T. This value is in good agreement with other SMMs.

The simulation of measured tunnel splittings for Mn_4 - ($S = 8$) is much easier because an integer spin is not very sensitive to transverse field components resulting from hyperfine and dipolar couplings. We found that a second order term with $E = 0.057$ K can describe well the data.

In conclusion, we have shown that the predicted spin parity effect [18, 19, 20] can indeed be observed by measuring the tunnel splitting as a function of transverse field. An integer spin system is rather insensitive to small transverse fields whereas a half-integer spin systems is much more sensitive. However, a half-integer spin system will also undergo tunneling at zero external field as a result of environmental degrees of freedom such as hyperfine and dipolar couplings or small intermolecular superexchange interaction.

I. Tupitsyn and M. Elhajal are acknowledged for fruitful discussions, and C. Thirion, D. Mailly and A. Benoit for support to the micro-SQUID technique. This work was supported by the European Union TMR network MOLNANOMAG, HPRN-CT-1999-0012.

-
- [1] R. Sessoli, D. Gatteschi, A. Caneschi, and M. A. Novak, *Nature* **365**, 141 (1993).
 - [2] M.A. Novak and R. Sessoli, in *Quantum Tunneling of Magnetization-QTM'94*, Vol. 301 of *NATO ASI Series E: Applied Sciences*, edited by L. Gunther and B. Barbara (Kluwer Academic Publishers, London, 1995), pp. 171–188.
 - [3] J. R. Friedman, M. P. Sarachik, J. Tejada, and R. Ziolo, *Phys. Rev. Lett.* **76**, 3830 (1996).
 - [4] L. Thomas, F. Lioni, R. Ballou, D. Gatteschi, R. Sessoli, and B. Barbara, *Nature (London)* **383**, 145 (1996).
 - [5] C. Sangregorio, T. Ohm, C. Paulsen, R. Sessoli, and D. Gatteschi, *Phys. Rev. Lett.* **78**, 4645 (1997).
 - [6] S. M. J. Aubin, N. R. Dilley, M. B. Wemple, G. Christou, and D. N. Hendrickson, *J. Am. Chem. Soc.* **120**, 839 (1998).
 - [7] A. Caneschi, D. Gatteschi, C. Sangregorio, R. Sessoli, L. Sorace, A. Cornia, M. A. Novak, C. Paulsen, and W. Wernsdorfer, *J. Magn. Magn. Mat.* **200**, 182 (1999).
 - [8] D. J. Price, F. Lioni, R. Ballou, P.T. Wood, and A. K. Powell, *Phil. Trans. R. Soc. Lond. A* **357**, 3099 (1999).
 - [9] J. Yoo, E. K. Brechin, A. Yamaguchi, M. Nakano, J. C. Huffman, A.L. Maniero, L.-C. Brunel, K. Awaga, H. Ishimoto, G. Christou, and D. N. Hendrickson, *Inorg. Chem.* **39**, 3615 (2000).
 - [10] L. Bokacheva, A.D. Kent, and M.A. Walters, *Phys. Rev. Lett.* **85**, 4803 (2000).
 - [11] W. Wernsdorfer, A. Caneschi, R. Sessoli, D. Gatteschi, A. Cornia, V. Villar, and C. Paulsen, *EuroPhys. Lett.* **50**, 552 (2000).
 - [12] W. Wernsdorfer, T. Ohm, C. Sangregorio, R. Sessoli, D. Mailly, and C. Paulsen, *Phys. Rev. Lett.* **82**, 3903 (1999).
 - [13] W. Wernsdorfer, R. Sessoli, and D. Gatteschi, *EuroPhys. Lett.* **47**, 254 (1999).
 - [14] W. Wernsdorfer, A. Caneschi, R. Sessoli, D. Gatteschi, A. Cornia, V. Villar, and C. Paulsen, *Phys. Rev. Lett.* **84**, 2965 (2000).
 - [15] A. Fort, A. Rettori, J. Villain, D. Gatteschi, and R. Sessoli, *Phys. Rev. Lett.* **80**, 612 (1998).
 - [16] E. M. Chudnovsky and D. A. Garanin, *Phys. Rev. Lett.* **79**, 4469 (1997).
 - [17] N.V. Prokof'ev and P.C.E. Stamp, *Phys. Rev. Lett.* **80**, 5794 (1998).
 - [18] J. L. Van Hemmen and S. Sütö, *EuroPhys. Lett.* **1**, 481 (1986).
 - [19] D. Loss, D. P. DiVincenzo, and G. Grinstein, *Phys. Rev. Lett.* **69**, 3232 (1992).
 - [20] J. von Delft and C. L. Henley, *Phys. Rev. Lett.* **69**, 3236 (1992).
 - [21] A. Garg, *EuroPhys. Lett.* **22**, 205 (1993).
 - [22] W. Wernsdorfer and R. Sessoli, *Science* **284**, 133 (1999).
 - [23] W. Wernsdorfer, M. Soler, G. Christou, and D.N. Hendrickson, *J. Appl. Phys.* **1**, 1 (2002).
 - [24] A. M. Gomes, M. A. Novak, W. Wernsdorfer, R. Sessoli, L. Sorace, and D. Gatteschi, *J. Appl. Phys.* **87**, 6004 (2000).
 - [25] S. Bhaduri, M. Pink, K. Folting, W. Wernsdorfer, and G. Christou, *J. Chem. Soc.* **1**, 1 (Dalton Trans submitted for publication.).
 - [26] L. Landau, *Phys. Z. Sowjetunion* **2**, 46 (1932).
 - [27] C. Zener, *Proc. R. Soc. London, Ser. A* **137**, 696 (1932).
 - [28] S. Miyashita, *J. Phys. Soc. Jpn.* **64**, 3207 (1995).
 - [29] S. Miyashita, *J. Phys. Soc. Jpn.* **65**, 2734 (1996).
 - [30] G. Rose and P.C.E. Stamp, *Low Temp. Phys.* **113**, 1153 (1998).
 - [31] M. Thorwart, M. Grifoni, and P. Hänggi, *Phys. Rev. Lett.* **85**, 860 (2000).
 - [32] M. N. Leuenberger and D. Loss, *Phys. Rev. B* **61**, 12200 (2000).
 - [33] Jie Liu, Biao Wu, Li-Bin Fu, Roberto B. Diener, and Qian Niu, *cond-mat/0105497* (2001).
 - [34] E. M. Chudnovsky and D. A. Garanin, *cond-mat/0105195* (2001).
 - [35] The Kramers theorem asserts that no matter how unsymmetric the crystal field, an ion possessing an odd number of electrons must have a ground state that is at least doubly degenerate, even in the presence of crystal fields and spin-orbit interactions [H. A. Kramers, *Proc. Acad. Sci. Amsterdam* **33**, 959 (1930)] The Kramers theorem can be found in standard textbooks on quantum mechanics L. D. Landau and E. M. Lifschitz, *Quantum Mechanics* (Pergamon, London, 1959).
 - [36] A more detailed study show that the tunnel splittings obtained by the Landau-Zener method are slightly influenced by environmental effects like hyperfine couplings [11]. Therefore, one might call it an effective tunnel splitting.
 - [37] The fit could be improved by using a combination of transverse terms but this does not lead to a better insight concerning the spin parity effect.